



INSTYTUT TECHNIKI BUDOWLANEJ
PL 00-611 WARSZAWA
ul. Filtrowa 1
tel.: (+48 22) 825-04-71
(+48 22) 825-76-55
fax: (+48 22) 825-52-86
www.itb.pl



Member of



www.eota.eu

European Technical Assessment

**ETA-12/0394
of 29/09/2017**

General Part

Technical Assessment Body issuing the European Technical Assessment

Instytut Techniki Budowlanej

Trade name of the construction product

RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W and RAWL RM50 / RAWL RM50-S / RAWL RM50-W

Product family to which the construction product belongs

Bonded anchor with anchor rod made of galvanized steel or stainless steel of sizes M8 to M30 for use in non-cracked concrete

Manufacturer

RAWLPLUG S.A.
ul. Kwidzyńska 6
51-416 Wrocław
Poland

Manufacturing plant

Manufacturing Plant no. 3

This European Technical Assessment contains

16 pages including 3 Annexes which form an integral part of this Assessment

This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of

Guideline for European Technical Approval ETAG 001, Edition April 2013 "Metal anchors for use in concrete – Part 1: Anchors in general and Part 5: Bonded anchors", used as European Assessment Document (EAD)

This version replaces

ETA-12/0394 issued on 28/06/2013

This European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and should be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may be made, with the written consent of the issuing Technical Assessment Body. Any partial reproduction has to be identified as such.

Specific Part

1 Technical description of the product

The RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W and RAWL RM50 / RAWL RM50-S / RAWL RM50-W are bonded anchors (injection type) consisting of an injection mortar cartridge using an applicator gun equipped with a special mixing nozzle and threaded anchor rod sizes M8 to M30 made of:

- galvanized carbon steel,
- stainless steel,
- high corrosion resistant stainless steel,

with hexagon nut and washer.

The threaded a rod is placed into a drilled hole previously cleaned and injected (using an applicator gun) with a mortar with a slow and slight twisting motion. The rod or rebar is anchored by the bond between rod, mortar and concrete.

The threaded rods are available for all diameters with three type of tip end: one side 45° chamfer, two sides 45° chamfer or flat. The threaded rods are either delivered with the mortar cartridges or commercial standard threaded rods purchased separately. The mortar cartridges are available in different sizes and types. The mortar cartridges are available in different sizes: 150 ml to 825 ml and types: two part foil capsules in one cartridge, coaxial cartridge, side by side cartridge or foil capsules.

An illustration and the description of the products are given in Annex A1 to A4.

2 Specification of the intended use in accordance with the applicable European Assessment Document (EAD)

The performances given in Section 3 are only valid if the anchors are used in compliance with the specifications and conditions given in Annex B1 to B5.

The performances given in this European Technical Assessment are based on an assumed working life of the anchor of 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer or the Technical Assessment Body, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Performance of the product

3.1.1 Mechanical resistance and stability (BWR 1)

The essential characteristic is detailed in the Annex C1 to C3.

3.1.2 Safety in case of fire (BWR 2)

No performance assessed.

3.1.3 Hygiene, health and the environment (BWR 3)

Regarding dangerous substances there may be requirements applicable to the products falling within its scope (e.g. transposed European legislation and national laws, regulations and administrative provisions). In order to meet the provisions of the Construction Products Regulation, these requirements need also to be complied with, when and where they apply.

3.1.4 Safety and accessibility in use (BWR 4)

For Basic Requirement Safety in use the same criteria are valid as for Basic Requirement Mechanical resistance and stability (BWR 1).

3.1.5 Sustainable use of natural resources (BWR 7)

No performance assessed.

3.2 Methods used for the assessment

The assessment of fitness of the anchors for declared intended use in relation to the requirements for mechanical resistance and stability and safety in use in the sense of the Basic Requirements 1 and 4 has been made in accordance with the ETAG 001 "Metal anchors for use in concrete", Part 1: "Anchors in general" and Part 5: "Bonded anchors", on the basis of Option 7.

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

According to Decision 96/582/EC of the European Commission the system of assessment and verification of constancy of performance (see Annex V to Regulation (EU) No 305/2011) given in the following table applies.

Product	Intended use	Level or class	System
Metal anchors for use in concrete	For fixing and/or supporting to concrete structural elements (which contributes to the stability of the works) or heavy units	-	1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document (EAD)



Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Instytut Techniki Budowlanej.

For type testing the results of the tests performed as part of the assessment for the European Technical Assessment shall be used unless there are changes in the production line or plant. In such cases the necessary type testing has to be agreed between Instytut Techniki Budowlanej and the notified body.

Issued in Warsaw on 29/09/2017 by Instytut Techniki Budowlanej



Anna Panek, MSc
Deputy Director of ITB

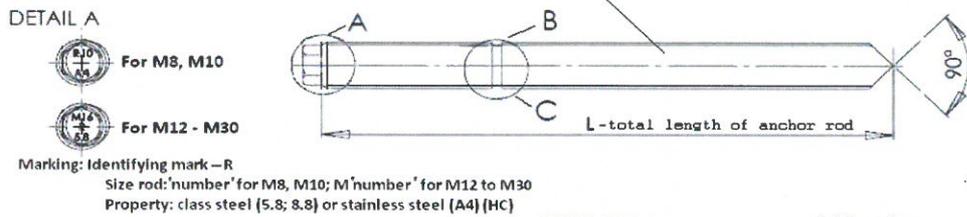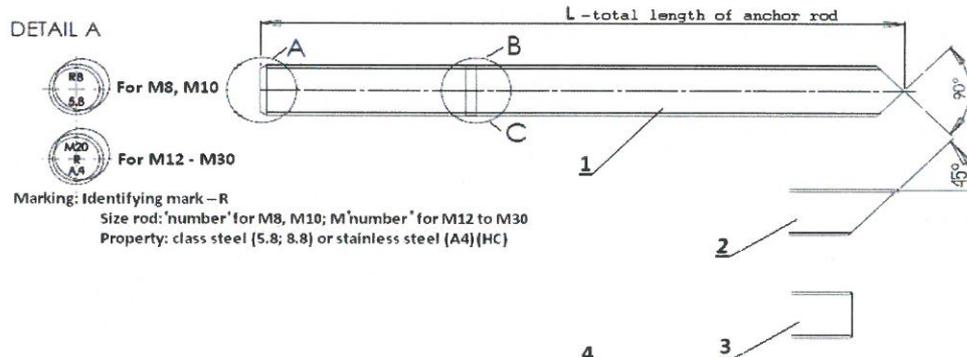

1. Anchor rod R-STUDS-(88),(A4),(HC)-FL
2. 45° shape with anchor rod
3. The flat end of anchor rod
4. Anchor rod R-STUDS-(88),(A4),(HC) with the hexagonal tip
5. Hexagonal nut
6. Washer

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Threaded anchor rod

Annex A1
of European
Technical Assessment
ETA-12/0394

Table A1: Threaded rods

Part	Designation		
	Steel, zinc plated	Stainless steel	High corrosio resistance stainless steel (HCR)
Threaded rod	Steel, property class 5.8 to 12.9, acc. to EN ISO 898-1; zinc plated $\geq 5 \mu\text{m}$ acc. to EN ISO 4042 or hot-dip galvanized $\geq 45 \mu\text{m}$ acc. to EN ISO 10684	Material 1.4401, 1.4404, 1.4571 acc. to EN 10088; property class 70 and 80 (A4-70 and A4-80) acc. to EN ISO 3506	Material 1.4529, 1.4565, 1.4547 acc. to EN 10088; property class 70 acc. to EN ISO 3506
Hexagon nut	Steel, property class 5 to 12, acc. to EN 898-2; zinc plated $\geq 5 \mu\text{m}$ acc. to EN ISO 4042 or hot-dip galvanized $\geq 45 \mu\text{m}$ acc. to EN ISO 10684	Material 1.4401, 1.4404, 1.4571 acc. to EN 10088; property class 70 and 80 (A4-70 and A4-80) acc. to EN ISO 3506	Material 1.4529, 1.4565, 1.4547 acc. to EN 10088; property class 70 acc. to EN ISO 3506
Washer	Steel, acc. to EN ISO 7089; zinc plated $\geq 5 \mu\text{m}$ acc. to EN ISO 4042 or hot-dip galvanized $\geq 45 \mu\text{m}$ acc. to EN ISO 10684	Material 1.4401, 1.4404, 1.4571 acc. to EN 10088; corresponding to anchor rod material	Material 1.4529, 1.4565, 1.4547 acc. to EN 10088; corresponding to anchor rod material

Commercial standard threaded rods (in the case of rods made of galvanized steel – standard rods with property class ≤ 8.8 only), with:

- material and mechanical properties according to Table A1,
- confirmation of material and mechanical properties by inspection certificate 3.1 according to EN-10204:2004; the documents shall be stored,
- marking of the threaded rod with the embedment depth.

Note: Commercial standard threaded rods made of galvanized steel with property class above 8.8 are not permitted in some Member States.

Table A2: Injection mortars

Product	Composition
RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W and RAWL RM50 / RAWL RM50-S / RAWL RM50-W	Bonding agent: polyester resin styrene free Hardener: dibenzoyl peroxide Additive: quartz sand Supplied in three colours: standard, grey (G) and stone (ST)


RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W and RAWL RM50 / RAWL RM50-S / RAWL RM50-W

Materials


Annex A2
of European
Technical Assessment
ETA-12/0394

Coaxial cartridge –

150 ml, 280 ml, 300 ml, 310 ml, 330 ml, 380 ml, 400 ml, 410 ml, 420 ml.

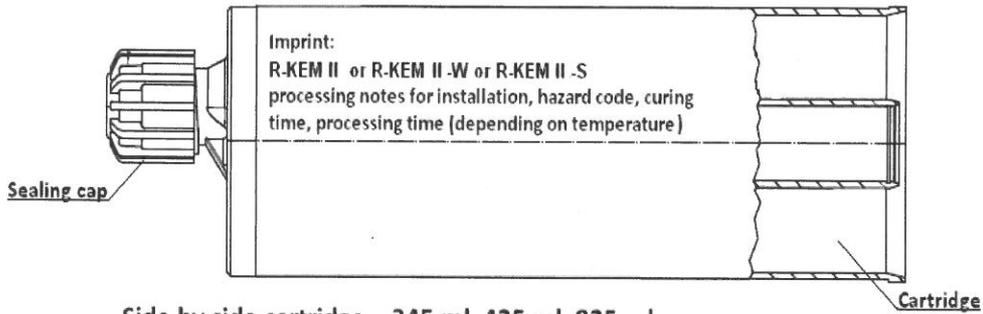


Side by side cartridge – 345 ml, 425 ml, 825 ml.

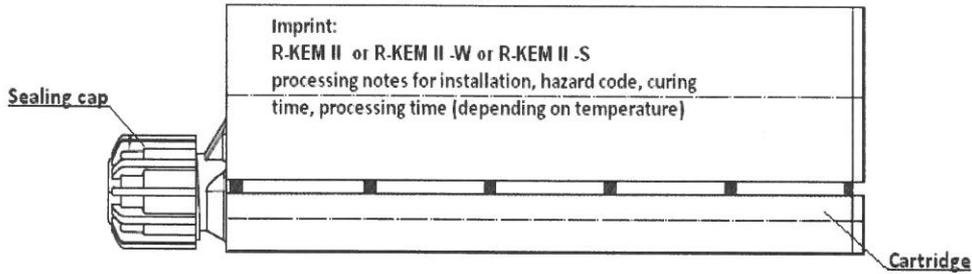


Cartridge a single component for two part foil capsules –

150 ml, 175 ml, 280ml, 300 ml, 310 ml, 380 ml, 400 ml, 550 ml, 600 ml.

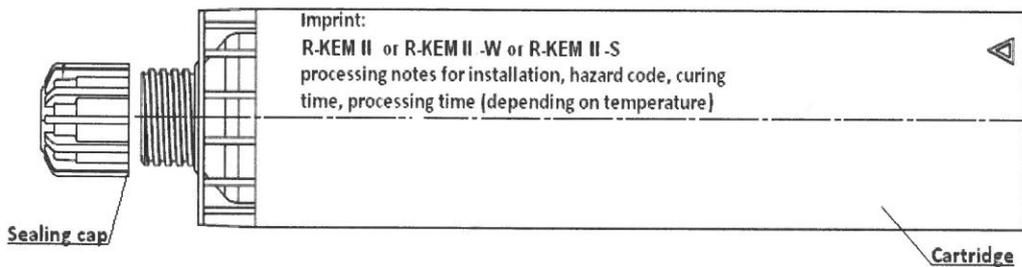

Mixer for cartridge




**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Cartridge types and sizes

Annex A3
of European
Technical Assessment
ETA-12/0394

Foil capsule (CFS system) –

150 ml, 175 ml, 280ml, 300 ml, 310 ml, 380 ml, 400 ml, 550 ml, 600 ml.

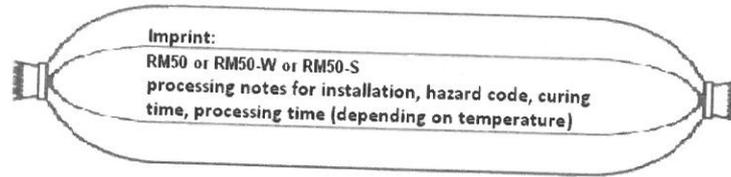


Mixer for foil capsule (CFS system)




Mixer standard plus adapter CFS+ for foil capsule



Gun for foil capsule (CFS system)

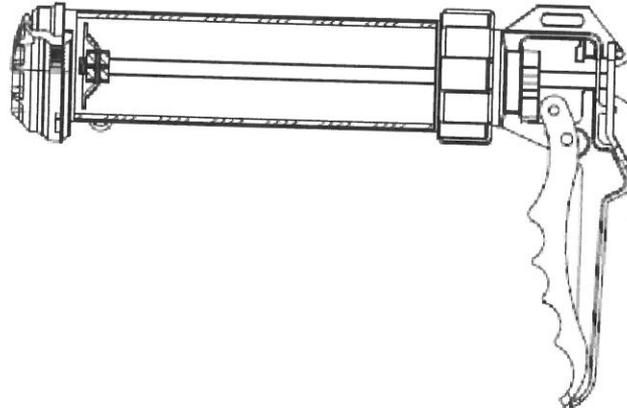

Gun for capsule (RAWL CFS +)

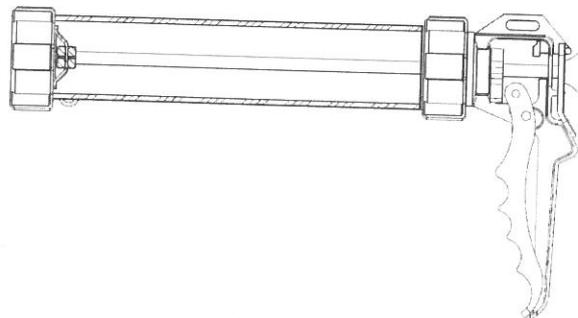

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Cartridge types and sizes

Annex A4
of European
Technical Assessment
ETA-12/0394

SPECIFICATION OF INTENDED USE

Use:

The anchors are intended to be used for anchorages for which requirements for mechanical resistance and stability and safety in use in the sense of the Basic Requirements 1 and 4 of Regulation (EU) 305/2011 shall be fulfilled and failure of anchorages made with these products would compromise the stability of the works, cause risk to human life and/or lead to considerable economic consequences.

Anchors subject to:

Static and quasi-static loads: sizes M8 to M30.

Base material:

- Reinforced or unreinforced normal weight concrete of strength class C20/25 at minimum to C50/60 at maximum according to EN 206-1.
- Non cracked concrete.

Temperature range:

The anchors may be used in the following temperature range:

- -40°C to +40°C (max. short term temperature +40°C and max. long term temperature +24°C).
- -40°C to +80°C (max. short term temperature +80°C and max. long term temperature +50°C).

Use conditions (environmental conditions):

- Elements made of galvanized steel may be used in structures subject to dry internal conditions.
- Elements made of stainless steel may be used in structures subject to dry internal conditions and also in concrete subject to external atmospheric exposure (including industrial and marine environment) or exposure in permanently damp internal conditions if no particular aggressive conditions exist. Such particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with extreme chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used).
- Elements made of high corrosion resistant steel may be used in structures subject to dry internal conditions and also in concrete subject to external atmospheric exposure or exposure in permanently damp internal conditions or in other particular aggressive conditions. Such particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used).

Installation:

- Dry or wet concrete (use category 1).
- Flooded holes with the exception of seawater (use category 2).
- The anchors are suitable for hammer drilled holes.

Design methods:

- EOTA Technical Report TR029 (September 2010) or CEN/TS 1992-4.

<p>RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W and RAWL RM50 / RAWL RM50-S / RAWL RM50-W</p>	<p>Annex B1 of European Technical Assessment ETA-12/0394</p>
<p>Intended use</p>	

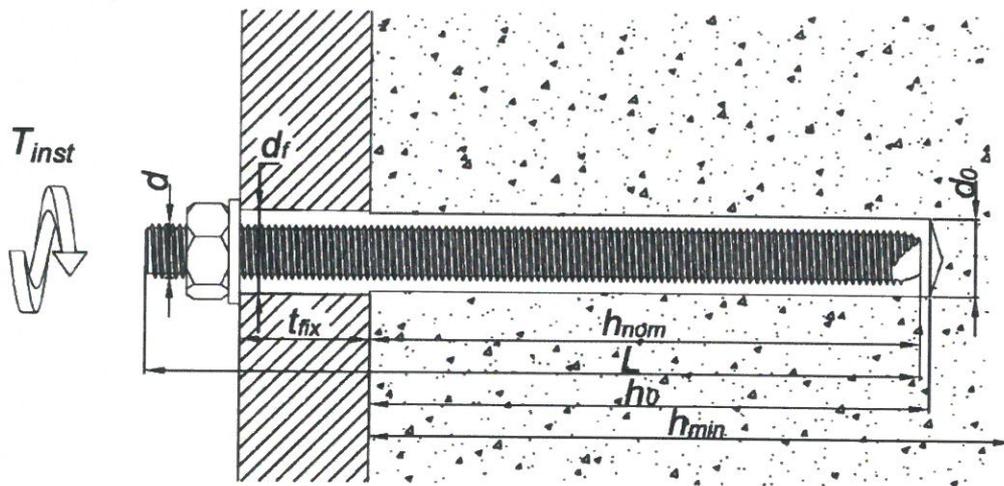


Table B1: Installation data - threaded anchor rod

Size		M8	M10	M12	M16	M20	M24	M30
Diameter of anchor rod	d [mm]	8	10	12	16	20	24	30
Nominal drilling diameter	d ₀ [mm]	10	12	14	18	24	28	35
Maximum diameter hole in the fixture	d _{fix} [mm]	9	12	14	18	22	26	32
Effective embedment depth	h _{ef,min} [mm]	60	70	80	100	120	140	165
	h _{ef,max} [mm]	100	120	145	190	240	290	360
Depth of the drilling hole	h ₀ [mm]	h _{ef} + 5 mm						
Minimum thickness of the concrete slab	h _{min} [mm]	h _{ef} + 2d ₀ ≥ 100 mm						
Torque moment	T _{inst} [N·m]	10	20	40	80	120	180	300
Minimum spacing	s _{min} [mm]	0,5 · h _{ef} ≥ 40 mm						
Minimum edge distance	c _{min} [mm]	0,5 · h _{ef} ≥ 40 mm						

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Installation data

Annex B2
of European
Technical Assessment
ETA-12/0394

Table B2: Processing time and minimum curing time

Mortar temperature	Concrete temperature	Processing time [min.]			Minimum curing time ¹⁾ [min.]		
		R-KEM II / RM50	R-KEM II-S / RM50-S	R-KEM II-W / RM50-W	R-KEM II / RM50	R-KEM II-S / RM50-S	R-KEM II-W / RM50-W
5°C	-20°C	-	-	45	-	-	1440
5°C	-15°C	-	-	30	-	-	1080
5°C	-10°C	-	-	20	-	-	480
5°C	-5°C	70	180	11	480	1440	300
5°C	0°C	45	120	7	240	1080	120
5°C	5°C	25	60	5	120	720	60
10°C	10°C	15	45	2	90	480	45
15°C	15°C	9	25	1,5	60	360	30
20°C	20°C	5	15	1	45	240	15
25°C	30°C	2	7	-	30	90	-
25°C	35°C	-	6	-	-	60	-
25°C	40°C	-	5	-	-	45	-


¹⁾ For wet condition and flooded holes the curing time must be double.

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Processing time and curing time


Annex B3
of European
Technical Assessment
ETA-12/0394

Additional mixer extension



Variable length from 300 mm up 1000 mm

Manual blower pump

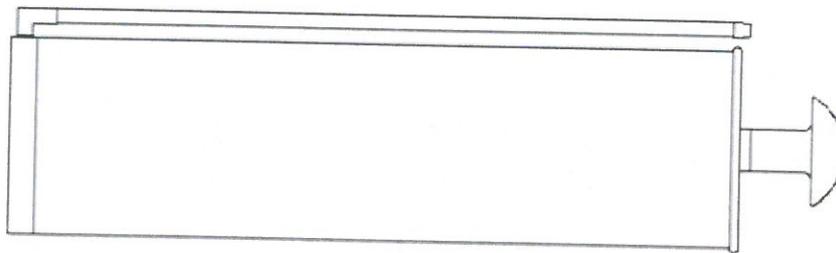

Steel brush










Table B3: Brush diameter

Size rod			M8	M10	M12	M16	M20	M24	M30
d_b	Brush diameter	[mm]	12	14	16	20	26	30	37

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Tools

Annex B4
of European
Technical Assessment
ETA-12/0394

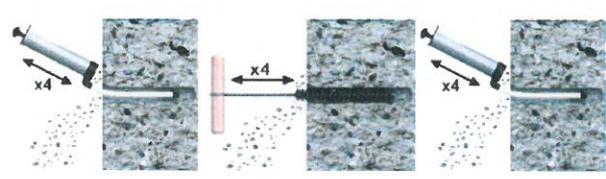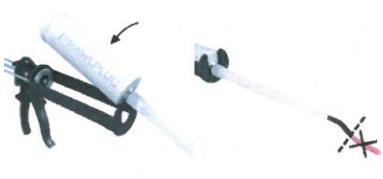	<p>1. Drill hole to the required diameter and depth using a rotary percussive machine.</p>
	<p>2. Hole cleaning. Clean the hole with brush and hand pump: <ul style="list-style-type: none"> - starting from the drill hole bottom blow the hole at least 4 times using the pump - using the specified brush, mechanically brush out the hole at least 4 times - starting from the drill hole bottom, blow at least 4 times with the pump. </p>
	<p>3. Insert cartridge into dispenser and attach nozzle. Dispense to waste until even colour is obtained.</p>
	<p>4. Insert the mixing nozzle to the far end of the hole and inject resin, slowly withdrawing the nozzle as the hole is filled to 2/3 of its depth.</p>
	<p>5. Immediately insert the stud, slowly and with slight twisting motion. Remove any excess resin around the hole before it sets.</p>
	<p>6. Leave the fixing undisturbed until the curing time elapses.</p>
	<p>7. Attach fixture and tighten the nut to the required torque.</p>

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Installation instruction

Annex B5
of European
Technical Assessment
ETA-12/0394

Table C1: Characteristic values for tension load for threaded rod in non cracked concrete

Size	M8	M10	M12	M16	M20	M24	M30		
Steel failure									
Steel failure with standard threaded rod grade 5.8									
Characteristic resistance	$N_{Rk,s}$	[kN]	18	29	42	78	122	176	280
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,50						
Steel failure with standard threaded rod grade 8.8									
Characteristic resistance	$N_{Rk,s}$	[kN]	29	46	67	126	196	282	449
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,50						
Steel failure with standard threaded rod grade 10.9									
Characteristic resistance	$N_{Rk,s}$	[kN]	37	58	84	157	245	353	561
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,40						
Steel failure with standard threaded rod grade 12.9									
Characteristic resistance	$N_{Rk,s}$	[kN]	44	70	101	188	294	424	673
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,40						
Steel failure with standard stainless steel threaded rod A4-70									
Characteristic resistance	$N_{Rk,s}$	[kN]	26	41	59	110	171	247	393
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,87						
Steel failure with standard stainless steel threaded rod A4-80									
Characteristic resistance	$N_{Rk,s}$	[kN]	29	46	67	126	196	282	449
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,60						
Steel failure with standard high corrosion threaded rod grade 70									
Characteristic resistance	$N_{Rk,s}$	[kN]	26	41	59	110	171	247	393
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,87						
Combined pull-out and concrete cone failure									
Characteristic bond resistance in non-cracked concrete C20/25									
Temperature range I: 40°C/24°C	$\tau_{Rk,ucr}$	[N/mm ²]	9,5	9,5	9,0	8,0	8,0	6,5	5,5
Temperature range II: 80°C/50°C	$\tau_{Rk,ucr}$	[N/mm ²]	8,0	8,0	7,5	7,0	6,5	5,0	4,5
Increasing factor for $\tau_{Rk,ucr}$ in non-cracked concrete	ψ_c	C30/37	1,04				1,0		
		C40/50	1,07				1,0		
		C50/60	1,09				1,0		
Partial safety factors for use category 1 + 2	$\gamma_{Mc} = \gamma_{Mp}$	[-]	2,1 ³⁾	1,8 ⁴⁾	1,8 ⁴⁾	1,8 ⁴⁾	1,8 ⁴⁾	1,8 ⁴⁾	1,8 ⁴⁾
Splitting failure									
Effective anchorage depth h_{ef}	min	[mm]	60	70	80	100	120	140	165
	max	[mm]	100	120	145	190	240	290	360
Edge distance	$c_{cr,N} = c_{cr,Np}$	[mm]	$c_{cr,Np} = \frac{s_{cr,Np}}{2}$						
	$c_{cr,sp}$ for h_{min}	[mm]	$2,5 \cdot h_{ef}$	$2,0 \cdot h_{ef}$	$1,5 \cdot h_{ef}$				
	$c_{cr,sp}$ for $h_{min} < h^{2)} < 2 \cdot h_{ef}$ ($c_{cr,sp}$ from linear interpolation)	[mm]							
	$c_{cr,sp}$ for $h^{2)} \geq 2 \cdot h_{ef}$	[mm]	$c_{cr,Np}$						
Spacing	$s_{cr,N} = s_{cr,Np}$	[mm]	$s_{cr,Np} = 20 \cdot d \cdot \left(\frac{f_{Rk,ucr}}{7,5} \right)^{0,5} \leq 3 \cdot h_{ef}$						
	$s_{cr,sp}$	[mm]	$2,0 \cdot c_{cr,sp}$						

¹⁾ in the absence of national regulations ²⁾ h – concrete member thickness ³⁾ $\gamma_2 = 1,4$ included ⁴⁾ $\gamma_2 = 1,2$ included
 Note: Design method according to TR 029

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
 and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Characteristic resistance under tension loads in non cracked concrete

Annex C1
 of European
 Technical Assessment
 ETA-12/0394

Table C2: Characteristic values for shear loads for threaded rod - steel failure without lever arm

Size			M8	M10	M12	M16	M20	M24	M30
Steel failure with standard threaded rod grade 5.8									
Characteristic resistance	$V_{Rk,s}$	[kN]	9	14	21	39	61	88	140
Partial safety factor	γ_{Ms}	[-]	1,25						
Steel failure with standard threaded rod grade 8.8									
Characteristic resistance	$V_{Rk,s}$	[kN]	15	23	34	63	98	141	224
Partial safety factor	γ_{Ms}	[-]	1,25						
Steel failure with standard threaded rod grade 10.9									
Characteristic resistance	$V_{Rk,s}$	[kN]	18	29	42	78	122	176	280
Partial safety factor	γ_{Ms}	[-]	1,50						
Steel failure with standard threaded rod grade 12.9									
Characteristic resistance	$V_{Rk,s}$	[kN]	22	35	51	94	147	212	337
Partial safety factor	γ_{Ms}	[-]	1,50						
Steel failure with standard stainless steel threaded rod A4-70									
Characteristic resistance	$V_{Rk,s}$	[kN]	13	20	29	55	86	124	196
Partial safety factor	γ_{Ms}	[-]	1,56						
Steel failure with standard stainless steel threaded rod A4-80									
Characteristic resistance	$V_{Rk,s}$	[kN]	15	23	34	63	98	141	224
Partial safety factor	γ_{Ms}	[-]	1,33						
Steel failure with high corrosion stainless steel threaded rod grade 70									
Characteristic resistance	$V_{Rk,s}$	[kN]	13	20	29	55	86	124	196
Partial safety factor	γ_{Ms}	[-]	1,56						

Table C3: Characteristic values for shear loads for threaded rod - steel failure with lever arm

Size			M8	M10	M12	M16	M20	M24	M30
Steel failure with standard threaded rod grade 5.8									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	19	37	65	166	324	561	1124
Partial safety factor	γ_{Ms}	[-]	1,25						
Steel failure with standard threaded rod grade 8.8									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	30	60	105	266	519	898	1799
Partial safety factor	γ_{Ms}	[-]	1,25						
Steel failure with standard threaded rod grade 10.9									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	37	75	131	333	649	1123	2249
Partial safety factor	γ_{Ms}	[-]	1,50						
Steel failure with standard threaded rod grade 12.9									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	45	90	157	400	779	1347	2699
Partial safety factor	γ_{Ms}	[-]	1,50						
Steel failure with standard stainless steel threaded rod A4-70									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	26	52	92	233	454	786	1574
Partial safety factor	γ_{Ms}	[-]	1,56						
Steel failure with standard stainless steel threaded rod A4-80									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	30	60	105	266	519	898	1799
Partial safety factor	γ_{Ms}	[-]	1,33						
Steel failure with high corrosion stainless steel threaded rod grade 70									
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	26	52	92	233	454	786	1574
Partial safety factor	γ_{Ms}	[-]	1,56						

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Characteristic resistance under shear loads in non-cracked concrete

Annex C2
of European
Technical Assessment
ETA-12/0394

Table C4: Concrete pry out failure and concrete edge failure

Size			M8	M10	M12	M16	M20	M24	M30
Effective anchorage depth h_{ef}	min	[mm]	60	70	80	100	120	140	165
	max	[mm]	100	120	145	190	240	290	360
Pry out failure									
Factor	k	[-]	2	2	2	2	2	2	2
Partial safety factor	γ_{Mp}	[-]	1,5						
Concrete edge failure: see clause 5.2.3.4 of Technical Report TR 029									
Partial safety factor	γ_{Mc}	[-]	1,5						

Table C5: Displacement under tension and shear loads

Size			M8	M10	M12	M16	M20	M24	M30
Characteristic displacement in non-cracked C20/25 to C50/60 concrete									
Admissible service load ¹⁾	F	[kN]	6,5	9,4	12,3	18,8	27,1	26,2	32,5
Displacement	δ_{N0}	[mm]	0,20	0,25	0,30	0,35	0,40	0,40	0,45
	$\delta_{N,c}$	[mm]	0,85	0,85	0,85	0,85	0,85	0,85	0,85

¹⁾ $F = F_{Rk} / \gamma_F \cdot \gamma_{Mc}$, with $\gamma_F = 1,4$

**RAWL R-KEM II / RAWL R-KEM II-S / RAWL R-KEM II-W
and RAWL RM50 / RAWL RM50-S / RAWL RM50-W**

Displacement under service loads: tension and shear loads

Annex C3
of European
Technical Assessment
ETA-12/0394